

# Photocatalytic Degradation of 2, 2, 4 Trimethyl Pentane (Isooctane) in Aqueous Solution

Felix A. Aisien<sup>1</sup>, Amabogha Blessing<sup>1</sup>

<sup>1</sup> Department of Chemical Engineering, University of Benin, Benin City, Edo Nigeria

## ABSTRACT

This work deals with photocatalytic degradation of 2, 2, 4 - trimethyl pentane (isooctane) in batchslurry photoreactor using solar radiation. The effect of various parameters such as pH, initial concentration of pollutant, catalyst dose, oxidant, and time variation were studied. The determination of the best catalyst was studied amongst the four catalysts (TiO<sub>2</sub>, ZnO, PSA and SSA). The kinetics of degradation of isooctane was also studied.

The results showed that TiO<sub>2</sub> was the best catalyst with a degradation rate of 57%. Also, the optimum conditions for the degradation of the isooctane were; 50mg/L of initial concentration, pH 8 and catalyst dose of 4.0g/l. The kinetics analysis for the degradation of isooctane revealed that it follows pseudo - first- order reaction kinetics. The Langmuir - Hinshelwood model showed a better fitting with reaction rate and adsorption equilibrium constants of 3.0 mg/L.h and  $1.53 \times 10^{-3}$  L/mg respectively and the regression was 0.979. Finally adsorption equilibrium isotherms study shows that degradation of isooctane pentane fits both Langmuir isotherm and Freundlich isotherm with maximum adsorption capacity of 18.12 mg/g and  $n = 2.26$  respectively.

**Keywords:** 2, 2, 4 trimethyl pentane (isooctane); Photocatalysis; TiO<sub>2</sub> catalyst

## Introduction

Photocatalysis has been proposed as an alternative for the treatment of organic pollutants in recent years as it is an attractive technique for the complete destruction of undesirable contaminants (pollutants) in liquid phase by using artificial light or solar illumination (1). It is a natural phenomenon in which a substance, termed the photo catalyzer, alters the speed of a chemical reaction through the action of light. By exploiting the energy of light, photo catalyzer induce the formation of strongly oxidizing reagents which can cause the decomposition of some organic and inorganic substances present in the water (2). The advantages of photocatalysis include low operation temperature, low cost and significantly low energy consumption. These factors have led to the relevant application of photocatalysis to the stage of commercialization (3). Photocatalytic processes are based on the generation of hydroxyl radicals HO (4-7).

The pollutant, isooctane is a colourless liquid with the odour of gasoline, it is also one of two chemicals used in establishing the octane rating for gasoline. The octane value is a number that

reflects the resistance of a gasoline mixture to knocking when used as fuel in an internal combustion engine. The source of isooctane is mainly from the production of petroleum products, it is also an organic pollutant that is very toxic and is easily found in the environment. Therefore, the photodegradation of 2, 2, 4 trimethyl pentane (isooctane) as the target compound in this study not only provide useful information for the treatment of isooctane but also it can be viewed as the primary method of inquiry for dealing with complicated organic pollutants.

Many examples of complete photo-oxidation of organic compounds have been reported. The photocatalytic degradation of some organics both in TiO<sub>2</sub> aqueous suspensions and over immobilized TiO<sub>2</sub> thin films have been studied (8).

In most of the above studies, Langmuir-Hinshelwood model was used to describe the degradation rate expressions in terms of the disappearance of compounds or the formation of CO<sub>2</sub> (9).

It has been demonstrated that catalyst dosage,

\* Corresponding author: Amabogha Blessing, Department of Chemical Engineering, University of Benin, Benin City, Edo Nigeria; Email: [bamabogha@yahoo.com](mailto:bamabogha@yahoo.com)

initial concentration of pollutants, effect of hydrogen peroxide, and pH of the solution are the main parameters affecting the degradation rate. It is well known that kinetic modelling of the photocatalytic process is essential to any practical applications (10).

The objective of this study is to degrade isooctane using solar radiation with different catalyst such as  $\text{TiO}_2$ , ZnO, Periwinkle shell and Snail shell ashes, to know the best catalyst for this study.

In this study, analysis was conducted to know the effects of operational parameters such as pH, initial concentration, oxidant and catalyst dose on the degradation rate. The adsorption of isooctane is further evaluated by the common isotherms (e.g., Langmuir, Freundlich isotherms) and kinetic models (e.g., Langmuir – Hinshelwood, pseudo – first – order, pseudo – second – order).

## Materials and Methods

### Materials

The photocatalyst  $\text{TiO}_2$  P-25 (mixture of Anatase and Rutile form of titanium dioxide in the ratio of 70:30), ZnO grade material 99% purity (Emory), was procured from Whosco Ventures Nigeria Limited. Periwinkle shell and snail shell ashes were prepared in the laboratory. Isooctane compound was purchased from Stanvac, hydrogen peroxide, (0.1, 1M) HCl and NaOH were obtained from Stanvac, distilled water was also used.

### Methods

The photocatalytic tests were conducted using the batch slurry system under light condition, it was carried out in order to evaluate the adsorption of isooctane on the surface of the four catalysts ( $\text{TiO}_2$ , ZnO, periwinkle shell and snail shell ashes), and so to obtain the most efficient catalyst needed for the study. Analysis contained fundamental parameters such as catalyst dosage, oxidant, pH, time variation and different initial concentrations of isooctane.

### Determination of the best catalyst

For this purpose, 100ml of the 200mg/L solution was taken and put into four conical flasks of 250ml, 5g the optimum amount of different catalysts was added ( $\text{TiO}_2$ , ZnO, periwinkle shell and snail shell ashes) into each of the conical flasks and shaken for 2hrs in the sun with an orbital shaker. The catalysts were filtered from the sample by Whatman filter paper (0.7 $\mu\text{m}$ ) then it was analyzed using UV – Vis spectrophotometer.

### Effect of Catalyst dose

In six conical flasks, 250ml of 200mg/L

isooctane solutions was placed with various catalyst doses of 2.0 – 12.0g/L of  $\text{TiO}_2$ , and they were shaken under the sun for 1h. The samples are filtered and analyzed with UV spectrophotometer to obtain optimum catalyst dose.

### Effect of initial concentration of Isooctane

Two hundred milliliter of 50 – 300mg/L of isooctane concentration was placed in six conical flasks. Then 4.0g/L titanium dioxide ( $\text{TiO}_2$ ) was added to each solution and exposed to the sun for a period of 1hr and analyzed to obtain optimum concentration.

### Effect of pH

One hundred milliliter of 50mg/L (best concentration) was placed in six conical flasks whose pH was adjusted using 0.5M HCL and 0.1M NaOH solution and then measured with pH meter. The pH values were varied from 2.0 – 12.0 and the samples were shaken under the sun for 2hrs; then they were filtered and analyzed to obtain optimum pH for best degradation rate.

### Effect of oxidant ( $\text{H}_2\text{O}_2$ )


One hundred milliliter of 50mg/L (best concentration) was placed in six conical flasks with catalyst dose of 4.0g/l  $\text{TiO}_2$ , at a pH of 8.0 and different volumes of hydrogen peroxide (2 – 12ml). Samples were analyzed to evaluate the effect of oxidant on photo degradation. Each of these samples was also placed on an orbital shaker, and was shaken for a period of 2 hrs, to allow equilibrium to be reached, and then it was filtered and analyzed with UV spectrophotometer.

### Effect of Exposure time

Two hundred milliliter of 50mg/L (best concentration) was placed in one conical flask adjusted to a pH of 8.0 (optimum pH) and fixed catalyst dose of 4.0g/L and then it was placed on an orbital shaker. The sample was shaken under the sun for 2 hrs. With an interval of 20mins for 10ml of sample to be withdrawn with a syringe, and then it was filtered and analyzed using UV spectrophotometer.

### Photocatalytic Degradation using solar radiation

In the analysis investigate photocatalytic degradation;  $\text{TiO}_2$  was used as photocatalyst because it was found to be the best among the other catalysts with a percentage degradation of 57%. In the analysis using solar radiation, 200ml of varying concentration (50 - 300 mg/L) of isooctane adjusted to a pH of 8.0 were placed in

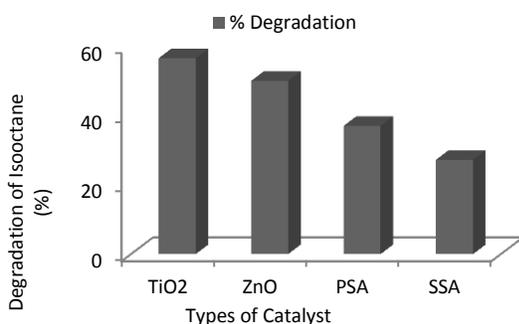

**Figure 1.** Percentage degradation of isooctane using different catalysts

six conical flasks, then 4.0g/l titanium dioxide (TiO<sub>2</sub>) was added to each solution and place on an orbital shaker. All samples were shaken with a regulated speed of 175 rev/min, under the sun, to allow the penetration of light for a period of 2hrs. With an interval of 20 min for 10ml of the sample to be taken with syringe, then they were filtered with Whatman filter paper (0.7µm) and analyzed with UV spectrophotometer with a wavelength of 246nm.

### Analysis

In using the UV spectrophotometer, it was switch on for at least 20mins to warm it up properly. After then, it was turn to the UV mode and the wavelength was adjusted to 246nm. A blank solution of 50% ethanol was prepared for zero checking the reading of the UV spectrophotometer. Then the filtered isooctane solution was poured into thoroughly washed glass Cuvette to at least 2/3 of its total height. One Cuvette is filled with the reference compound and the other one with the compound (ethanol) whose absorbance has to be measured at λ max. The Cuvette was placed in the Cuvette chamber inside the UV machine and the lid was closed. Then, the absorbance reading was displayed on the screen and it was recorded. To get the relationship between concentration and absorbance of the compound, a calibration curve is made. Calibration solutions are made from standard solutions with known concentration. The absorbance is plotted against known concentration of the samples. This standard curve is used to calculate the value of concentration of unknown sample from the absorbance reading. This was repeated for each of the filtered sample taken after time t and the results were recorded.

## Results and Discussion

### Effect of Catalyst Type


The catalyst efficiency of TiO<sub>2</sub>, ZnO, PSA and SSA were 57%, 50%, 37% and 27.3% respectively.

As a result the rate of degradation of isooctane was observed to be decreasing; this tells that UV from the sun increased the rate of degradation of isooctane. TiO<sub>2</sub> was the best catalyst compared to the other catalysts. In the case of the commercial and the local catalysts, among commercial catalysts (TiO<sub>2</sub>, ZnO) the rate of degradation with using TiO<sub>2</sub> was higher than ZnO and among local catalyst (PSA, SSA) PSA was more effective than SSA.

### Effect of Catalyst dosage

Photocatalyst (TiO<sub>2</sub>) dosage was varied from 2.0g/l to 12g/l during reactions for studying the isooctane degradation rate at different concentrations. It was observed that degradation rate of isooctane increases with increase in catalyst dose and becomes constant above a certain level as shown in (Figure 2) and after one particular optimize dose the degradation rate of the isooctane starts to decrease. The reasons for this decrease in degradation rate are:

- Aggregation of TiO<sub>2</sub> particles at high concentrations causing a decrease in the number of surface active sites and
- Decrease in opacity and light scattering of TiO<sub>2</sub> particles at high concentration. Therefore the optimum dose at which the highest degradation was observed was 4g/l

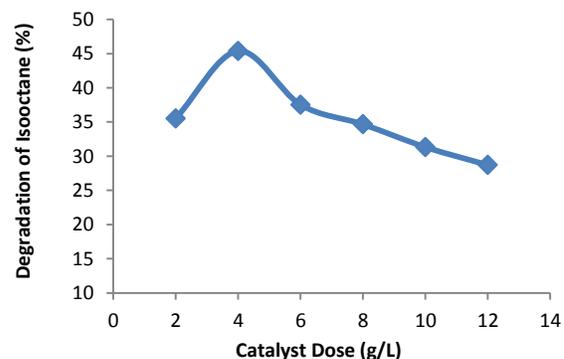


**Figure 2.** Percentage degradation of isooctane for varied catalyst dose (TiO<sub>2</sub>)

### Effect of Initial Concentration

Initial concentration was varied from 50 – 300mg/L, at constant catalyst dose of 4g/L. It was observed from the graph (Figure 3) that increasing concentration of compound solution from 50 to 300mg/L decreases the percentage of degradation rate and it was found that at 50mg/L concentration, degradation was 88.3% at 246nm and for 300mg/L compound concentration, percentage of degradation was reduced to 62.2% at 246nm. The reason behind this behavior may be due to the increase in the extent of adsorption


on the catalytic surface at reference compound concentration which reduces the catalytic activity of  $\text{TiO}_2$ . The increases in the isooctane solution concentration also decrease the path length of photon entering into the solution. Therefore 50mg/L was the optimal concentration with a percentage degradation of 88.3%.

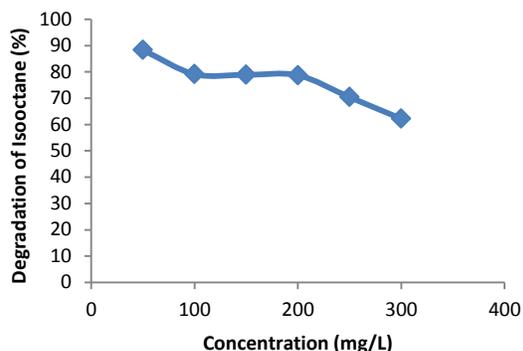

**Figure 3.** Percentage of degradation of isooctane for varied initial concentration using  $\text{TiO}_2$  catalyst dose of 4.0g/L

#### Effect of pH

The pH was varied from 2–12. The result shown in Figure 4 indicates that degradation increases with an increase in solution pH from 2 to a range of 8, and then led to a drastic decrease which result implies that the degradation of isooctane was favorable at alkaline conditions, and the optimum initial pH of solution is 8 (63.03%). This may be due to the fact that pH affects the state of reaction in solution and catalyst surface.

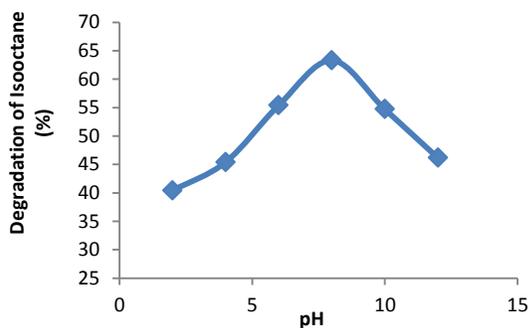


**Figure 4.** Effect of initial pH on photocatalytic degradation of isooctane for the Conc. = 50mg/L  $\text{TiO}_2$  = 4.0g/L

#### Effect of Oxidant ( $\text{H}_2\text{O}_2$ )

Another important data from these experiments is the effect of adding hydrogen peroxide. As it is shown in Figure 5, the addition of hydrogen peroxide has a positive effect on the degradation. The experiment was conducted by varying the hydrogen peroxide volume from 2.0 to 12 ml per 200ml of the isooctane sample. It was observed that the degradation of isooctane sample


increased with increase of oxidant, showing that the use of  $\text{TiO}_2$  by adding hydrogen peroxide molecules to generate hydroxyl radicals is more effective for this photocatalyst.

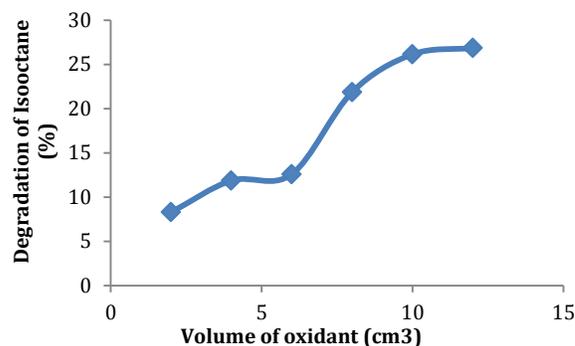

**Figure 5.** Percentage degradation for varying volume of oxidant ( $\text{H}_2\text{O}_2$ ) using  $\text{TiO}_2$  Catalyst

#### Effect of Time Variation

Figure 6 shows the percentage of degradation of isooctane at pH 8.0, and with 50mg/L concentration for varying time using  $\text{TiO}_2$  catalyst dose of 4.0g/L. It can be clearly seen that under light radiation with increasing the time of irradiation up to 2h, the amount of isooctane increased from 0 - 56.3%, almost in the proportion to the irradiation time in the investigated period. This is because that with an increase in irradiation time the photons absorbed on the surface of the photocatalyst becomes greater which in turn helps in the photocatalytic process.

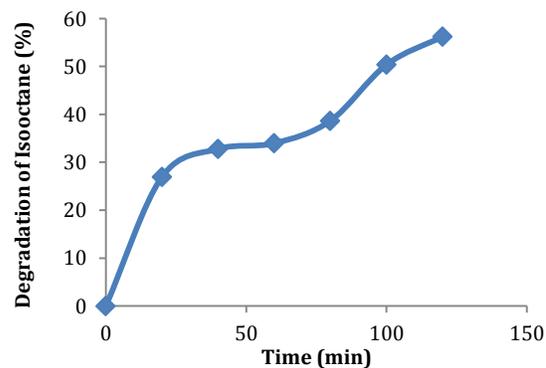

**Figure 6.** Percentage degradation of isooctane at pH 8.0 for varied time using  $\text{TiO}_2$  catalyst dose of 4.0g/L

#### Kinetics and Modeling of Photocatalytic Process

The destruction rates of organics in photocatalytic oxidation have been modeled by different kinetic models. Langmuir-Hinshelwood (L-H) kinetics seems to describe many of the reactions fairly well. The rate of destruction is given by Eq.1:

$$\frac{-dC}{dt} = \frac{k_1 k_2 C}{(1+k_2 C)} \quad (1)$$

In the ideal case, for which the L-H model is derived, C is the bulk solute concentration, k1 is the reaction rate constant, k2 is the equilibrium adsorption constant and t represents time. The L-H reaction rate constants are useful for comparing the reaction rate under different experimental conditions. Adsorption of organic substrate onto the catalyst can be modeled by mathematical models such as Langmuir and Freundlich model.

The mathematical formulae of Langmuir and Freundlich models are shown in Eqn. (2) and (3) respectively; both equations can be rewritten into linear form as shown in Eqn. 4 and Eqn. 5 respectively.

$$q_e = \frac{q_m K_L C_e}{1 + K_L C_e} \tag{2}$$

$$q_e = K_F C_e^{1/n} \tag{3}$$

$$\frac{C_e}{q_e} = \frac{1}{q_m} C_e + \frac{1}{K_L q_m} \tag{4}$$

$$\ln q_e = \ln K_F + \frac{1}{n} \ln C_e \tag{5}$$

Where

$K_F$ =Freundlich constant for adsorption capacities (L/mg)

$K_L$ =Langmuir constant (L/mg)

$1/n$ =Freundlich exponent (surface heterogeneity)

**Table 1.** Linear regression analysis of kinetics of isooctane degradation


Conc. (mg/L)	Pseudo-first order		Pseudo - second order	
	-r = KC		-r = KC <sup>2</sup>	
	$\ln \frac{C_0}{C} = K_1 t$	$\frac{1}{C} - \frac{1}{C_0} = K_2 t$		
	$K_1 \times 10^{-3}$	r <sup>2</sup>	$K_2 \times 10^{-5}$	r <sup>2</sup>
50	142	0.766	1.0	0.694
100	48	0.991	70	0.926
150	59	0.869	70	0.809
200	54	0.927	60	0.904
250	73	0.986	70	0.974
300	61	0.989	50	0.973

**Kinetics and Modeling**

Table 2 shows the linear regression analysis of the kinetics of isooctane degradation using photocatalysis. These results were used to analyze the rate of adsorption and possible adsorption mechanism of isooctane into TiO<sub>2</sub> catalyst using pseudo-first-order and pseudo-second-order models. From the above Table, the first order regression range from 0.766 - 0.991 while the second order range from 0.694 - 0.974. Hence, pseudo first order gave a better regression. As the result, the photodegradation of isooctane follows the Pseudo - first order.

**Langmuir - Hinshelwood Model**

The results confirmed the Langmuir-Hinshelwood relationship and indicated that adsorption represents the initial step in the

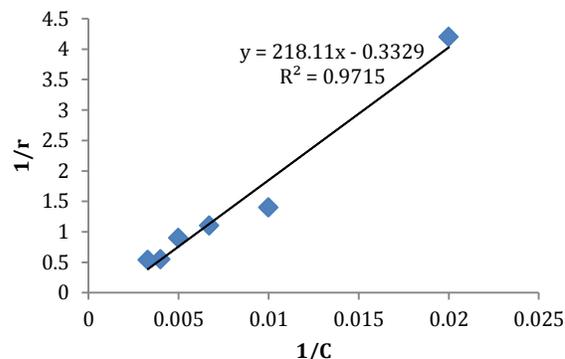

**Figure 7.** Langmuir - Hinshelwood model for the photodegradation of isooctane using TiO<sub>2</sub> catalyst


**Table 2.** Reaction rate, Equilibrium constants and regression for isooctane using Titanium dioxide (TiO<sub>2</sub>)

Equations	Reaction rate and adsorption equilibrium constants		Regression
$r = \frac{kK_{LH}}{1 + kK_{LH}}$	$K_{LH}$ (mg/L.h)	k (L/mg)	r <sup>2</sup>
$\frac{1}{r} = \frac{1}{kK_{LH}} \frac{1}{C} + \frac{1}{K_{LH}}$	3.00	$1.53 \times 10^{-3}$	0.9715

photocatalytic process. The k and  $K_{LH}$  values calculated from the slope of the straight line ( $r^2 = 0.9715$ ) and from the ordinate, were  $1.53 \times 10^{-3}$  L/mg and 3.00 mg/L.h respectively. Hence the value for adsorption is lesser than  $K_{LH}$  for reaction. This implies that degradation was basically result of reaction and the photocatalytic degradation of isooctane under optimized working conditions which follows satisfactorily the Langmuir - Hinshelwood model. This explanation is similar to that reported by Guetta *et al* 2005 (11).

**Adsorption Isotherms**

In order to evaluate the efficacy of the photodegradation procedure, the equilibrium adsorption of isooctane was studied as a function of equilibrium concentration. Adsorption isotherms were studied to estimate the adsorption capacity. The adsorption process of isooctane was tested with Langmuir and Freundlich isotherm models.

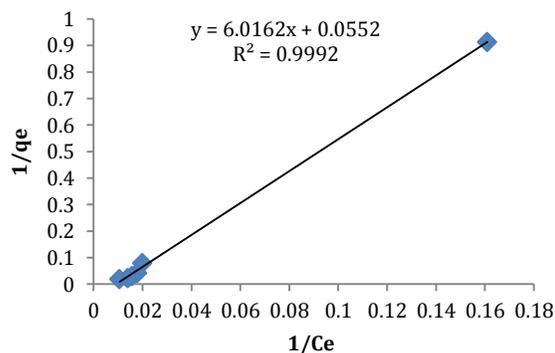

**Figure 8.** Langmuir Isotherm

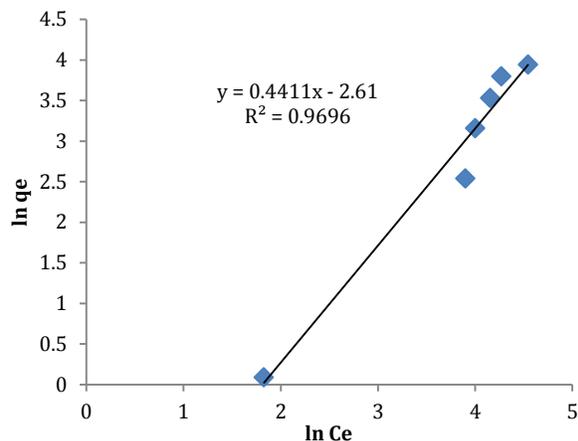


Figure 9. Freundlich Isotherm

Figure 8 shows the Langmuir Isotherm. From the plot, the maximal adsorption quantity ( $q_m$ ) and the Langmuir adsorption constant ( $K_L$ ) were found to be 18.12 mg/m<sup>2</sup> and  $9.175 \times 10^{-3}$  L/mg

respectively. Also, Figure 9 shows the Freundlich Isotherm. From the plot, the Freundlich adsorption constant ( $K_F$ ) was found to be 0.07353 L/mg and  $n$  to be 2.26. This explanation is similar to that reported by Alina *et al* 2011 (12).

The isotherm models gave good correlation coefficients with  $r^2 \geq 0.999$ . The applicability of the two isotherm models implies that both monolayer adsorption (that is only a limited number of surface sites as adsorbing sites for the isooctane molecules) and heterogeneous surface conditions exist under studied experimental conditions.

**Adsorption Kinetic Modeling**

Several Kinetic models are used to explain the adsorption mechanism. Pseudo - first order and Pseudo - second - order kinetics allow the computation of the first and second order constant,  $k_1$  and  $k_2$  and of linear regression correlation coefficient,  $r^2$ .

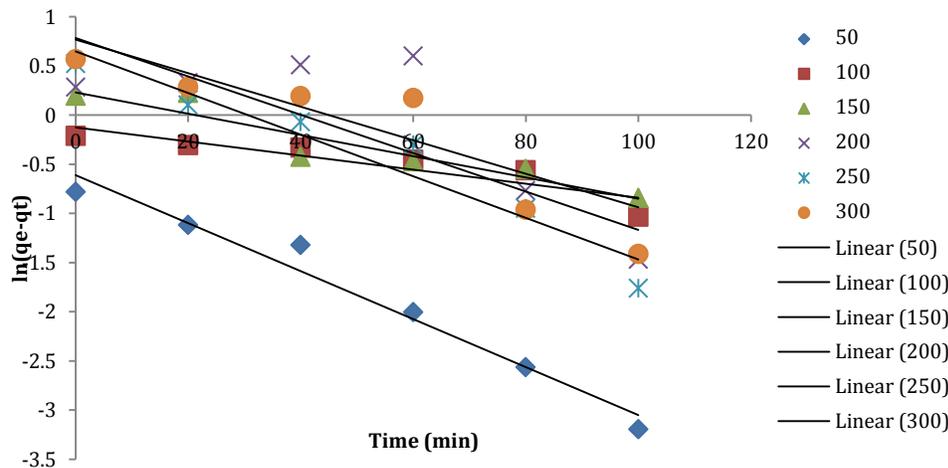


Figure 10. Pseudo - first - order reaction kinetics for isooctane adsorption on TiO<sub>2</sub> catalyst. Condition: pH 8.0, catalyst dosage 4g/L

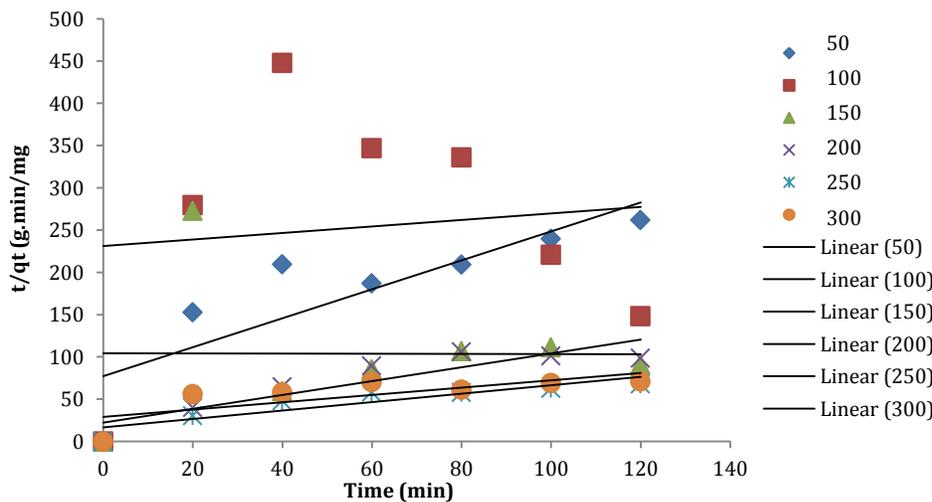


Figure 11. Pseudo - second - order reaction kinetics for isooctane adsorption on TiO<sub>2</sub> catalyst. Condition: pH 8.0, catalyst dosage 4g/L

**Table 3.** Equilibrium constants for the Pseudo first and second order model

Adsorption model	Pseudo-first-order	Pseudo-second-order		
Equation	$\frac{dq_t}{dt} = k_{e1}(q_e - q_t)$	$\frac{dq_t}{dt} = k_{e2}(q_e - q_t)^2$		
Linear form	$= \ln(q_e - q_t) = \ln(q_e) - k_{e1}t$	$\frac{t}{q_t} = \frac{1}{k_{e2}q_e^2} + \frac{t}{q_e}$		
Plot	$\ln(q_e - q_t)$ against $t$	$\frac{t}{q_t}$ against $t$		
Conc. (mg/L)	$k_{e1}$	$r^2$	$k_{e2}$	$r^2$
50	0.0242	0.971	1.142	0.726
100	0.0071	0.814	0.255	0.013
150	0.01	0.921	0.536	0.777
200	0.014	0.900	0.547	0.815
SS250	0.0214	0.931	0.332	0.807
300	0.0194	0.943	0.289	0.558

From the above Table, it can be deduced that pseudo - first- order model fits the photodegradation of isooctane on TiO<sub>2</sub> catalyst with r<sup>2</sup> range of 0.814 - 0.971 which is far better than the pseudo - second - order model with r<sup>2</sup>range of 0.013 - 0.815.

## Conclusions

Photocatalytic process can efficiently degrade isooctane using sunlight radiation source. The observations, clearly demonstrated the importance of choosing optimum degradation parameters to obtain high degradation rates which is most essential for any practical applications of photocatalytic oxidation processes. The optimum conditions for photo degradation of isooctane are 4g/L catalyst dose, 50mg/L concentration, and 8.0 pH.

The photocatalytic degradation of isooctane using TiO<sub>2</sub> catalyst under solar radiation followed Langmuir-Hinshelwood kinetics with reaction rate and adsorption equilibrium constant of 3.00mg/L.min and 1.52 x 10<sup>-3</sup>L/mg respectively.

Also the Adsorption isotherm study showed that degradation of isooctane fit both Langmuir

isotherm and Freundlich isotherm with maximum adsorption capacity of 18.12mg/g and n = 2.26, respectively.

It also showed that pseudo - first- order model fits the photodegradation of isooctane on TiO<sub>2</sub> catalyst with r<sup>2</sup> range of 0.814 - 0.971 which is far better than the pseudo - second - order model with r<sup>2</sup> range of 0.013 - 0.815. From the results so far, isooctane was concluded to be a rapidly degrading organic compound.

## Acknowledgement

The authors would like to thank from all coworkers that help us to this Research.

## References

1. Zhao N, Zhang T, Oyama T, Horikoshi S, Serpone J, Hidaka H. Applied Catalysis B: Environmental. 2003; 42:13.
2. Blanco JG. Solar Detoxification, Head of Solar Chemistry, United Nations Educational, Scientific and Cultural Organization. 2003; 93-135.
3. He C, Yu Y, Hu X, Larbot A. Influence of silver doping on the photocatalytic activity of titania films. Applied Surface Science. 2002; 200(1): 239-47.
4. Okamoto KI, Yamamoto Y, Tanaka H, Tanaka M, Itaya A. Heterogeneous photocatalytic decomposition of phenol over TiO<sub>2</sub> powder. Chem Soc Jpn. 1985; 58 (7): 2015-22.
5. Ahmed S, Ollis DF. Solar Energy 1984, 32, 597.
6. Al-Ekabi H, Serpone N. J Phys Chem. 1988; 92: 5726.
7. Serpone N. J. Photochem. Photobiol. 1996; 93: 199.
8. Matthews RW. Wat. Res. 1990; 24: 653.
9. Pelizzetti E, Serpone N, Ah-You YK, Tran TP, Harris R, Hidaka H. Solar Energy 1987; 39: 491.
10. Pruden AL, Ollis DF. Catal J. 1983; 82: 404.
11. Guettaï N, Ait AH. Photocatalytic oxidation of methyl orange in presence of Titanium dioxide in aqueous suspension. Part II: kinetics study. Desalination. 2005; 185(1):439-48.
12. Alina Catrinellon I Ion, A Culetu. Mat. sci. Eng. B, 2011; 176(6):504-9.